

Experience gained from Fire Tests according to EN 45 545-2 and DIN 5510- 2 for Testing of Seats:

EN 45 545-2/ISO 5658-2 and ISO 5660-1 DIN 5510-2

Prof. Dipl. Ing. Dr. Dieter HOHENWARTER

Head of Fire Testing Laboratory

Federal Institute of Technology (tgm)
Plastics Technology and Environmental Engineering

CONTENTS

1. **Introduction to fire tests according to EN 45 545-2**
 - 1.1 Fire tests according to ISO 5658-2: 2006
 - 1.2 Fire tests according to ISO 5660-1: 2002
2. **Examples of Fire Tests according to ISO 5658-2 and ISO 5660-1**
 - 2.1 GFK Material 4 mm with glas fibre + polyester resin
 - 2.2 Material named GFK Pulturdat thickness 2.9 mm
 - 2.3 Sandwich door leaf for railway application
3. **Combustibility of seats according to DIN 5510-2**
 - 3.1 ÖBB seats without and with flame retardent covering of the foam
 - 3.2 Comparison of one covering material with different foams
 - 3.3 New test method for seats worked out at CEN/TC 256/WG01N 021
4. **Conclusion**
 - 4.1 Fire test of materials according to ISO 5658-2 and ISO 5660-1
 - 4.2 Fire behaviour of seats

See also...

Presentation [C]

...in **APPENDIX.**

(C)opyright IFV Bahntechnik

1. Introduction to fire tests according to EN 45 545-2 (ISO 5658-2:2006, ISO 5660-1:2002)

In the past, materials were investigated according to the old Austrian Standard VORNORM ÖNORM B 3800-2 (Behaviour of building materials and components in fire; building materials: requirements and tests; 1. 12. 1988) regarding the designation low combustibility (combustibility class B1) and moderately combustible (combustibility class B2) including the characteristics such as smoke production and droplet formation at the TGM fire testing laboratory.


After the catastrophic fire of the Kaprun glacier funicular 2 in 2000, the work environment and the fire safety investigation of constituents of coaches was substantially expanded. It liaises with the fact that all interior fittings of coaches of the ÖBB were fire-safety tested approximately in accordance with DIN 5510-2. Shortly after the incident of Kaprun, all components were tested and found to correspond to the interior fittings of coaches ÖBB the fire safety requirements approximately according to DIN 5510-2 (Preventive fire protection in railway vehicles – Part 2: Fire behaviour and fire side effects of materials and parts; classification, requirements and test methods, Draft February 1996).

The fire testing of materials according to EN 45 545-2 (Railway applications – Fire protection on railway vehicles, Part 2: Requirements for fire behavior of material and components, March 2013) is done according to ISO 5658-2 (Reaction to fire tests – Spread of flame – part 2: Lateral spread on building and transport products in vertical configuration: 2006) and ISO 5660-1 (Reaction-to-fire tests – Heat release, smoke production and mass loss rate – Part 1: Heat release rate; cone calorimeter method: 2002) and is carried out at the fire testing laboratory. The toxicity tests and smoke tests according to ISO 5659-2 (Plastics – smoke generation – Part 2: Determination of optical density by a single-chamber test: 2006) are done by another institute (ofi) in Vienna. Concerning the tests of ISO 5658-2 and ISO 5660-1 we are an approved fire laboratory by CERTIFER (Railway Certification Agency) allowed to perform tests according to EN 45 545-2.

1.1 Fire Test according to ISO 5658-2:2006

The testing according to ISO 5658-2 specifies a method of testing for measuring the lateral spread of flame along the surface of a specimen of a product orientated in the vertical position. It provides data suitable for comparing the performance of essentially flat materials, composites or assembly that are used primarily as the exposed surface of walls in buildings or transport vehicles, such as ships and trains.

A test specimen (800 mm x 155 mm) is placed in a vertical position adjacent to a gas-fired radiant panel where it is exposed to a defined field of radiant heat flux for a time of 10 minutes. Following ignition, any flame front that develops is noted and the results are expressed in terms of flame spread distance and at least the critical heat flux at extinguishment (CFE).

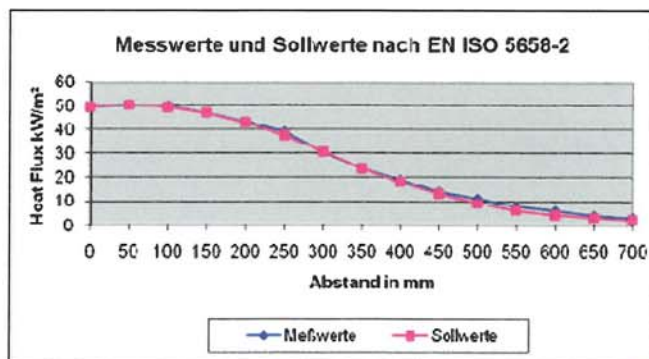

The correlation between flame spread distance and CFE is shown in the diagram above.

(C)opyright IFV Bahntechnik


1.2 Fire Test according to ISO 5660-1:2002

The test according to ISO 5658-2 specifies a method for assessing the heat release rate of a specimen exposed in the horizontal orientation to controlled levels of irradiance with an external igniter. The test method is based on the observation that, generally, the net heat of combustion is proportional to the amount of oxygen required for combustion. Approximately 13.1 MJ of heat are released per kilogram of oxygen consumed. During the test specimens are burned under ambient air conditions (radiation in the range of 0 to 100 kW/m²) and at the same time oxygen concentration and exhaust gas flow rates are measured. Using these measurements the Average Rate of Heat Emission (ARHE) and then the Maximum Average Rate Heat Emission MARHE are calculated.



The principle of the MARHE Calculation is shown in the following diagram.

The calculation of MARHE from the measured heat release rate (HRR measured in kW/m²).

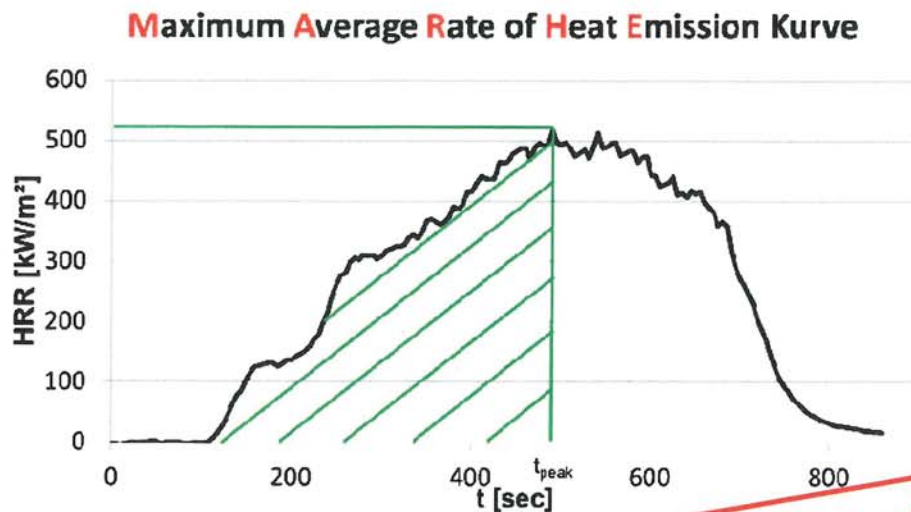

(C)opyright IFV Bahntechnik

2. Examples of Fire Tests according to ISO 5658-2 and ISO 5660-1



In the following a number of examples of tests according to the mentioned standards are presented. Fire tests of materials according to EN 45 545-2 are carried out according to ISO 5658-2 and ISO 5660-1.

2.1 GFK Material 4 mm with glas fibre + polyester resin

The testing of this GFK Material shows a significant difference of the heat release rate measured according to ISO 5660-1 between the outside and the rear side of the material. The outside shows a significant influence of the painting and gel coat while the heat release rate of the rear side is influenced by the top coat. In the following the results of 3 measurements per sample (diagrams) are shown.

GFK outside (green painted front side)
Gel coat
MAHRE 62 kW/m²

GFK rear side (grey color)
Top coat
MAHRE 78 kW/m²

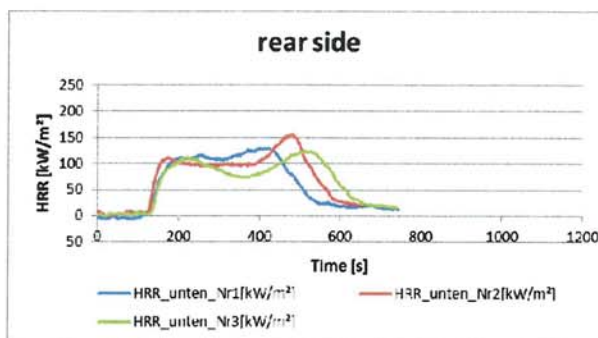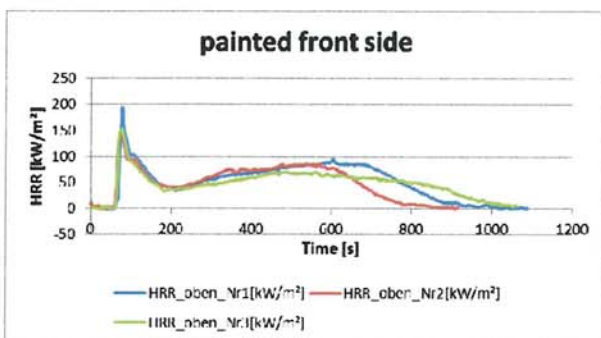

The spread of flame testing according to ISO 5658-2 of this GFK material shows no significant difference between both of the different sides of the material.

GFK green outside CFE =22 kW/m²

GFK grey inside CFE =22 kW/m²



(C)opyright IFV Bahntechnik

2.2 Material named GFK Pultrudat thickness 2.9 mm


The testing of this GFK material was made for research purposes.

*Laminate
Reinforcement glass fiber roving
– E-glass
Glass fiber mats
Matrix unsaturated polyester resin with
Lp for high surface quality halogenfree
Surface polyester veil on visual outside of the
profile
Fiber weight content 48% tolerance ± 5%
Profiles were painted*



The picture shows the GFK material before and after the Cone test with the different layers of the glass fibre roving.

This material was radiated with different radiation intensities to study the heat release rate of this GFK material. It is clear that another heat radiation intensity yields to a different time when the material ignites. The time to ignite the material depends on the heat radiation intensity which is analyzed later.

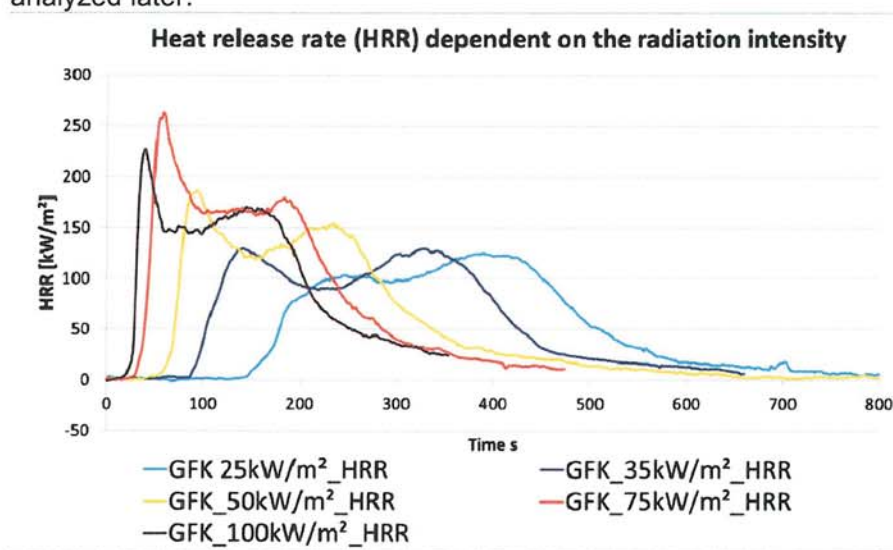

The results in figure above show that, in general, shortly after the ignition at higher radiation intensities, a large amount of heat is released. Upon irradiation with 75 kW/m² the highest amount of heat (HRR peak) is released and on exposure to 100 kW/m² a smaller amount of heat (HRR peak) than at 75 kW/m² is measured, as can be seen in the following table.

This can be explained as follows: Upon irradiation with 100 kW/m² the heating leads to (short) strong fumes (outgassing) almost simultaneously with the ignition of the material and thus the heat release is reduced. Upon irradiation with 75 kW/m², however, a rather uniform smoke formation takes place as may be seen from the figure of the smoke production rate dependent on the heat radiation intensity.


Likewise, the respectively extinction-coefficient and the temperature of the surface were measured during the tests with different heat radiation intensities. The extinction coefficient is proportional to the smoke production.

(C)opyright IFV Bahntechnik

What is noticeable about this GFK - product is that, strong fumes (outgassing) form up at the beginning even before ignition. The outgassing is caused by low molecular weight molecule fractions which evaporate before. This brief strong degassing takes place, especially in the middle of the plate so that the specimen is deformed (just before the inflammation) in a small area and a noticeable sound is heard as well.

The following two diagrams show the measurement of the
 Temperature °C: **blue line**
 Extinction coefficient 1/m (Smoke production) **black line**
 Heat release rate HRR kW/m² **red line**
 dependent on time and is shown for 2 different radiation intensities.

The material ignites approximately at a temperature of 340 °C.

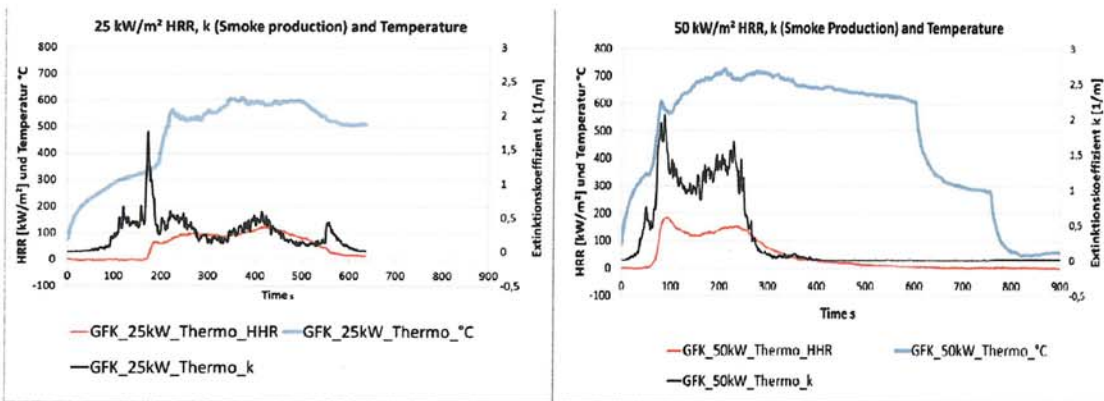

In the following table the results of measurements with a Cone calorimeter of a GFK product at different radiation intensities are presented.

- HRR - Heat release rate (kW/m²)
- HRR peak - Peak heat release rate (kW/m²)
- EHC - Effective heat of combustion per mass (MJ/kg)
- SPR - Smoke production rate (m²/s)

Radiation intensity [kW/m ²]	MARHE [kW/m ²]	HRR peak [kW/m ²]	EHC [MJ/kg]	SPR [m ² /s]	Time to ignite [s]	Burning Time [s]
25	67	133	20.0	0.0083	143	395
35	81	132	19.6	0.0091	82	363
50	104	181	19,1	0.0119	48	316
75	145	263	19.4	0.0179	23	335
100	137	227	18.7	0.0225	18	284

The time until the ignition of the material depends on the radiation intensity which is shown in the table above. When radiated with high intensity, the material ignites very quickly, while the exposure to low-intensity takes longer to achieve ignition. In the following figure (left side) this relationship is shown graphically.

(C)opyright IFV Bahntechnik


From the literature [James G. Quintiere: Principles of Fire Behavior, Delmar Cengage Learning, 1998] the following relationship results

$$t_{\text{ignition}} = C \cdot k \cdot \rho \cdot c \left[\frac{T_{\text{ignition}} - T_{\text{ambient}}}{\text{Heat Flux}} \right]^2$$

C constant, k thermal conductivity, ρ density, c specific heat


T_{ignition} Temperature at ignition, T_{ambient} ambient temperature, heat flux – radiation intensity

The transformation of the equation above, for the relationship between the radiation intensity and the square root of the inverse t_{ignition} (time to ignition) results in a linear relationship. In the following diagram on the right side this relationship is shown and it shows up as the theoretically expected linear dependence.

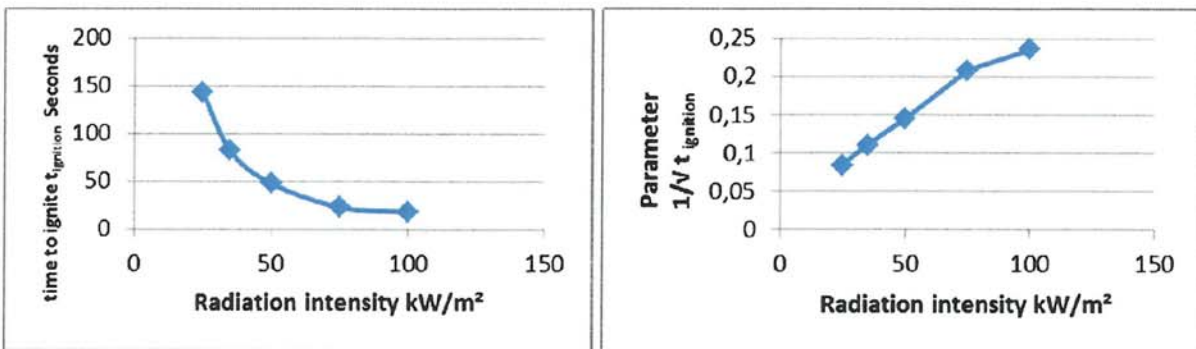


The time to ignite is dependent on radiation intensity and the radiation intensity depends nearly linear on the parameter 1/√t_{ignition}.

The following figure shows that during a short time relatively strong fume (extinction-coefficient) is evident especially when radiated with 100 kW/m², whereas at the other radiation intensities a more uniform smoke production can be detected during a longer time range.

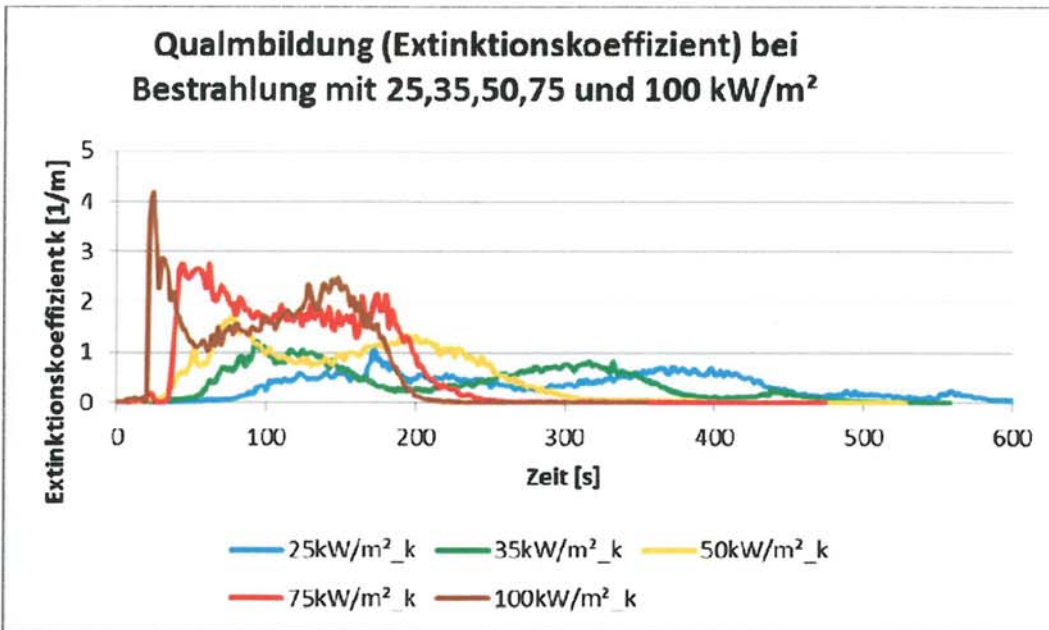


(C)opyright IFV Bahntechnik

With the results of the table above the smoke production rate (SPR) increases approximately proportional to the intensity of irradiation which the following figure shows.

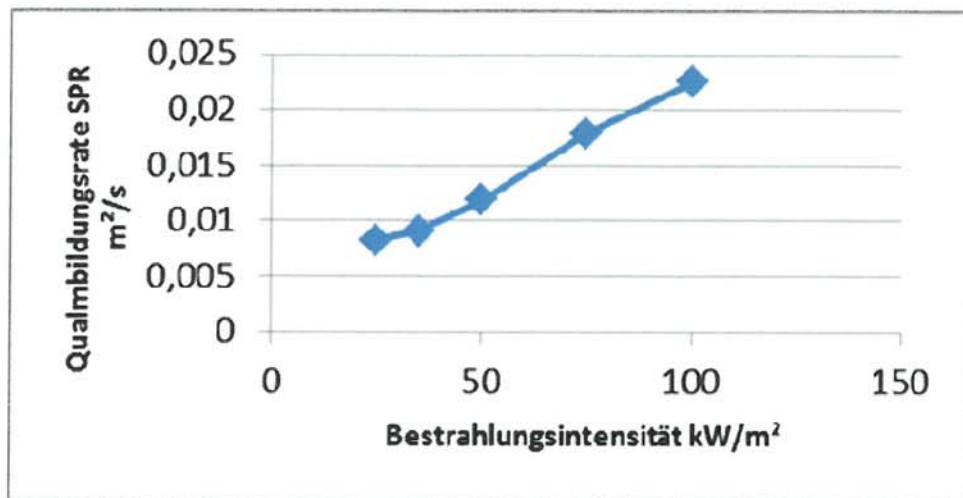

2.3 Heat release rate of PMMA dependent on the radiation intensity

Tests of a PMMA material were carried out for own research purposes. The following figure shows the heat release rate for different radiation intensities in the range of 15 kW/m² to 100 kW/m². These different radiation intensities which ignite the material occur at different time spans.

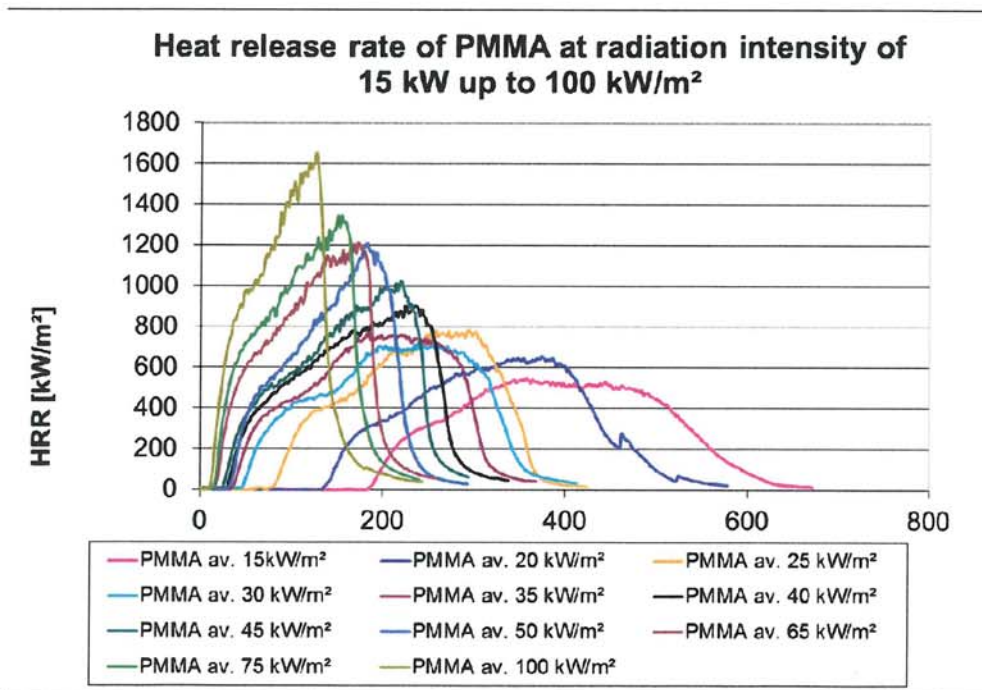


From the literature [James G. Quintiere: Principles of Fire Behavior, Delmar Cengage Learning, 1998] the following relationship is used to show the relation between the time to ignite (t_{ignition}) and the heat flux which correspond to the heat radiation intensity.

$$t_{\text{ignition}} = C \cdot k \cdot \rho \cdot c \left[\frac{T_{\text{ignition}} - T_{\text{ambient}}}{\text{Heat Flux}} \right]^2$$

C constant, k thermal conductivity, ρ density, c specific heat
 T_{ignition} temperature at ignition,
 T_{ambient} ambient temperature, heat flux – radiation intensity

(C)opyright IFV Bahntechnik

As expected from the equation there is (nearly) a linear correlation between the time to ignite and the square of the radiation intensity (diagram on the right side).

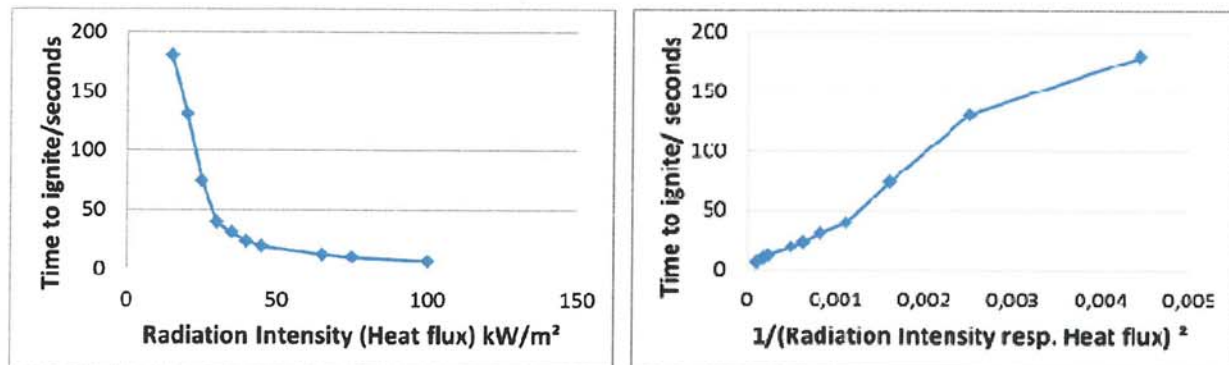

2.3 Sandwich door leaf for railway application


According to DIN 5510-2: 2009 metals and alloys with organic coatings with a nominal thickness <0.3 mm are considered as components with proven requirements and therefore they do not need to be tested (DIN 5510-2, Chapter 5.4).

According to EN 45545-2: 2013, the walls of external body shells (including painting/coating systems, films and windows) must be checked according to requirement R7. The fulfillment of the requirements of EN 45545-2 must be demonstrated by the manufacturer of such coatings.

One of these test results are shown below: The test of this Sandwich door leaf was commissioned by Knorr-Bremse GmbH, IFE Kematen Division Door Systems.

The sandwich door consists of the following components:



- Coated, faced aluminium honeycomb product 19.8 kg/m²
- Final coating: 2K HS Clear coat 50 µm
- Second coating: Basecoat 10 - 20 µm
- First coating: Water based 2-K Epoxy Primer 40 µm
- Facing: Aluminium coil coated 40 µm
- Honeycomb: 0,029 kg/dm³, thickness 30 mm, cell diameter 19 mm, wall thickness 0.071 mm
- Adhesive: Epoxy adhesive 0.2 mm
- Facing: Aluminium 1mm

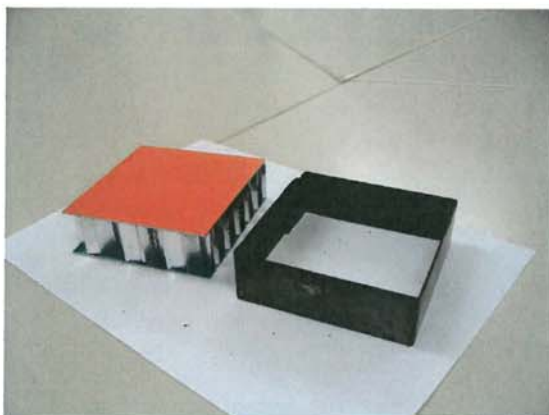

Test material for the cone test (with honeycomb structure) and for spread of flame test (closed structure).

(C)opyright IFV Bahntechnik

For the cone test the honeycomb was tested with a frame shown in the following picture.

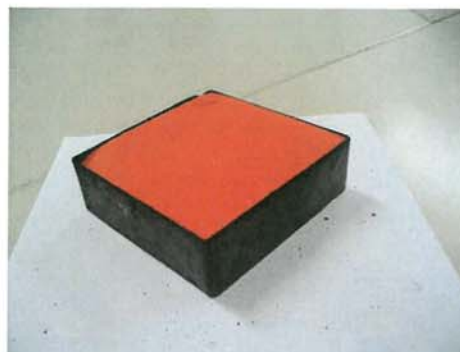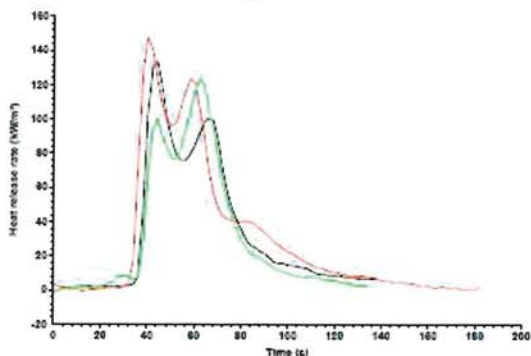

Heat release rate ISO 5660-1:2002

MARHE: < 50 kW/m²



Lateral spread of flame ISO 5658-2

CFE >20 kW/m²

{Many thanks to Knorr-Bremse GmbH Division IFE Automatic Door Systems for the permission to publish the above mentioned results.}

3. Combustibility of seats according to DIN 5510-2

The fire performance of seats for railway cars is tested using original complete seats according to DIN 5510-2.

Upholstered seats must be self-extinguishing, even if the seat covering is slit open (vandalised). A 100 g paper cushion is positioned on the seat base (see picture on the right).



(Draft) E DIN 5510-2:1996

Ventilation system: The hood can be operated so that the smoke produced during the experiment can be just sucked off.

DIN 5510-2: 2009

Ventilation system: The volume flow should be in the range of 0.5 to 0.7 m³/s. The ventilation system is calibrated with n-Heptan. The smoke production rate should be calculated from the measured extinction coefficient.

3.1 ÖBB seats without and with flame retardant covering of the foam


The fire testing of the seats from the Austrian Railway coaches was carried out for the ÖBB in the year 2008 and shows that in this case a flame retardant covering was necessary to protect the foam.

Seat *without* flame retardant covering of the foam.

Fire extinguisher was used after 13 minutes.



Seat *with* flame retardant covering of the foam.

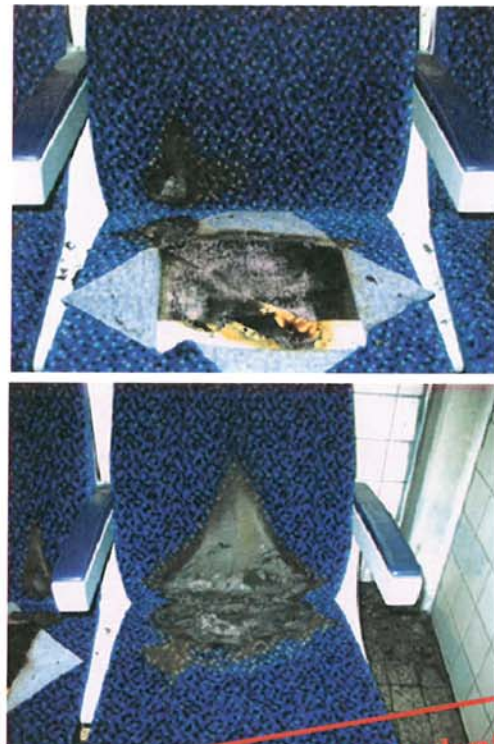

(C)opyright IFV Bahntechnik

3.2 Comparison (according to DIN 5510-2) of one covering material with different foams (ÖBB)

These tests to analyse which foam is compatible with the standard textile covering material used by the ÖBB, were made in the year 2005.

In order to analyze the behaviour of the foam the textile covering material was cut (vandalised).

Textile covering material: Producer Kneitz, velour chess 85% wool, 15 % polyamide (Velourstoff Schach 85% Wolle, 15 % Polyamid)

The following foams were tested:

Producer	Name of the foam
Purtec	Purtec 500
Metzler	Metzoprotect Qualität FRM-U FT3307
Weserland	Weserland Qualität FSF 710 RA
Weserland	Weserland PU Muster W 5662/1
Eurofoam	LS. NR. 04004452 Qualität KF 55 B1 weiß

The sequence of the products mentioned in the table above does not correspond with the sequence of the pictures of the seats in the following two picture lines.

The result of this research is: one combination of fabric upholstery (textile covering) with foam leads to a full-scale fire while a different combination of foam and textile covering extinguishes after 4 about minutes.

Fire extinguisher used after
10 Minutes



Self-extinguishing after
4:25 Minutes



Self-extinguishing after
6:48 Minutes



(C)opyright IFV Bahntechnik

Self-extinguishing after
4:00 minutes



Self-extinguishing after
4:57 minutes



Many thanks to ÖBB-Technische Services, Flottenengineering Nahverkehrs-Reisezugwagen (Manfred Schorm), St. Pölten for the permission to publish the above mentioned results.

3.3 New test method for seats worked out at CEN/TC 256/WG 01 N 021

CEN TC 256 work on the new standard "Railway applications - Fire protection on railway vehicles - Fire behaviour test on complete seats for railway vehicles". This new standard is based on the fire measurement method for seats used in EN 45 545-2:2013.

It is useful to separate the fire testing of seats used in EN 45 545, because there is only one test procedure included in EN 45545-2. Otherwise only the requirements for the flammability of the components of passenger railway vehicles are included.

This paper is based on the knowledge of this new standard of February 2015. This new standard is based on EN 45545-2:2013, but is improved in several positions.

The now valid EN 45545-2:2013 contains a flame exposure of the seats with a power of 7 kW, which corresponds to the burning power of 20 g newsprint. The seat testing according to DIN 5510-2 is carried out with a cushion of 100 g paper, and leads to a much stronger fire load of the seats. According to the new seat fire test standard, the specimen must be flamed with a burner power 28 kW for one minute and it must then be switched to 7 kW for 2 minutes.

Testing with vandalism

Four fire tests are required if the following conditions apply:


- the seat specification requires the seat to be vandalised
or
- the results of the (vandalism) procedure shows that the seat can be fully or partially vandalised,

The test program shall be as follows:

- a) Two fire tests shall be undertaken with the seat in a vandalised condition.
- b) Two fire tests shall be undertaken, with the seat in a not vandalised condition.

(C)opyright IFV Bahntechnik

In addition, some changes in the test apparatus are planned to increase the measurement accuracy because the current measurements according to EN 45545-2 contain a large measurement inaccuracy.

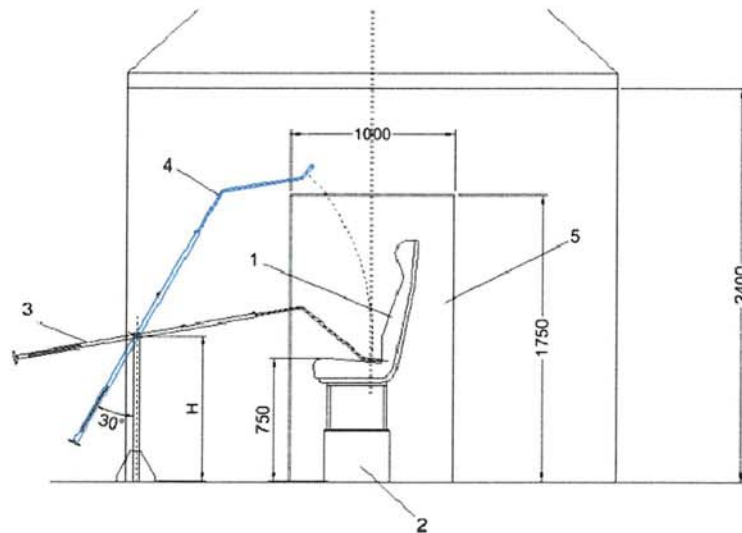

Position of the burner and the seat

4. Conclusion

4.1 Fire tests of materials according to ISO 5658-2 and ISO 5660-1

The test of a special GFK material shows a significant difference of the heat release rate measured according to ISO 5660-1 between the painted side and the rear side of the material.

Another GFK material was radiated with different radiation intensities which lead to different ignition times. This correlation fulfills the equation of the theory of fire behaviour for the ignition of thick materials. The tests for PMMA show also a good correlation between measurements and (fire) theory.

According to DIN 5510-2: 2009 metals and alloys with organic coatings with a nominal thickness of <math><0.3\text{ mm}</math> are considered as components with proven requirements and therefore do not need to be tested. But according to EN 45545-2: 2013 the walls of external body shells (including painting/coating systems, films and windows) must be checked according to requirement R7. As an example the results of one painting are shown.

4.2 Fire behaviour of seats

Fire behaviour of seats depends on:

- **Density of the foam:** Density 95 kg/m^3 is better than usual 85 kg/m^3 , however foams with 75 kg/m^3 can also fulfill the requirements
- **Flame retardant fibres** „glued“ on the foam can improve the fire behaviour of the seat
- **Combination of the textile covering and the foam:**
One textile/foam combination leads to full fire, while with another combination stops the fire after 4 Minutes

(C)opyright IFV Bahntechnik

Summary

Results of fire tests according to ISO 5658-2 and ISO 5660-1 are shown for different products. The results of GFK products are extensively analysed. The result of a body shell painting is analysed according to ISO 5658-2 and ISO 5660-1, but this painting, does not have to be analysed according to DIN 5510-2. Different possibilities to improve the fire behaviour of railway coaches are presented as well as the fact that the combination of the foam and the textile covering is essential.

Zusammenfassung

Die Ergebnisse von Brandversuchen nach ISO 5658-2 und ISO 5660-1 werden dargestellt und brandtechnische Untersuchungen von GFK Produkten ausführlich analysiert. Eine Wagenaußenlackierung wurde nach ISO 5658-2 und ISO 5660-1 geprüft, während diese Wagenaußenlackierung nach DIN 5510-2 **nicht** brandtechnisch untersucht hätte werden müssen. Verschiedene Möglichkeiten zur Verbesserung des Brandverhaltens von Eisenbahnsitzen werden dargestellt. Es wird auch gezeigt, dass die Kombination von Sitzbezug und Schaum für das Brandverhalten von Sitzen entscheidend ist.

Contact details of the AUTOR:**Prof. Dipl. Ing. Dr. Dieter HOHENWARTER**

Position: Head of Fire Testing Laboratory,
Organisation: Federal Institute of Technology (tgm)
Plastics Technology and Environmental Engineering
Address: A 1200 Wien, Wexstraße 19-23
Phone: +43 1 33 1 26 650
E-mail: dhohenwarter@tgm.ac.at
Internet: www.kunststoff.ac.at

© Copyright 2015


Schriftenreihe BAHNTECHNIK AKTUELL (Band 54 / 2015)

„FIRE SAFETY 2015“

Alle Rechte beim Verlag des IFV Bahntechnik e.V., Salzufer 17 - 19, SG 20, 10587 Berlin
www.fachpublikationen-online.de >>> ISBN 978-3-940727-47-3**(C)opyright IFV Bahntechnik**

BAHNTECHNIK AKTUELL
Schriftenreihe des
Interdisziplinären
Forschungsverbundes
Bahntechnik e.V.
54 / 2015
(Railway-Network Proceedings)

Tagungsdokumentation des
7. internationalen Fachsymposiums
FIRE SAFETY IN RAILWAY SYSTEMS
zum Thema Bahn-Brandschutz

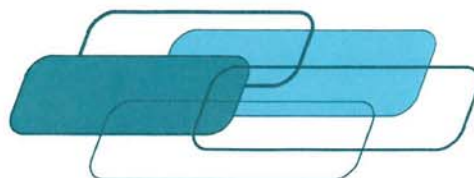

ifv Bahntechnik

Interdisziplinärer
Forschungs-
verbund
Bahntechnik e.V.

7th International Symposium

FIRE SAFETY IN RAILWAY SYSTEMS

Vienna
26 - 27 March 2015



www.railway-network.eu/fire-safety

Partner des Bahn-Brandschutz-Symposiums FIRE SAFETY.

WAGNER®



RSI
RAIL SERVICES INTERNATIONAL

Verlag des IFV BAHNTECHNIK e.V. © 2015
WWW.FACHPUBLIKATIONEN-ONLINE.DE
ISBN 978-3-940727-47-3

Copyright IFV Bahntechnik

VERLAG / PUBLISHER: Interdisziplinärer Forschungsverbund Bahntechnik e.V.

FIRE-SAFETY IN RAILWAY SYSTEMS 2015:
BAHN-BRANDSCHUTZ bei Schienenfahrzeugen und Bahn-Bauwerken
Tagungsdokumentation des 7. Internationalen Fachsymposiums zum Thema
BAHN-BRANDSCHUTZ bei Schienenfahrzeugen und Bahn-Infrastruktur
am 26. - 27. März 2015 in Wien

Hrsg.
Körperschaft: Interdisziplinärer Forschungsverbund Bahntechnik e.V.
Verlag: IFV Bahntechnik e.V.
Verlagsort: Berlin
Auflage: 1. Auflage, 2015
Reihe: BAHNTECHNIK AKTUELL
Band 54, Jahrgang 2015 (proceedings in english language)
ISBN: 978-3-940727-47-3

HERAUSGEBER / EDITOR

Leitender Herausgeber: Dipl.-Volkswirt Eckhard SCHULZ

Interdisziplinärer Forschungsverbund Bahntechnik e.V.
Salzufer 17 - 19, SG20
10587 Berlin / Germany
Telefon: 030 31473807 bzw. Telefax: 030 31425452
E-Mail: REDAKTION@IFV-BAHNTECHNIK.DE

1. Auflage, März 2015

PRINTED IN GERMANY

by IFV BAHNTECHNIK e.V., Salzufer 17 - 19 / SG20, 10587 Berlin / Germany
www.IFV-BAHNTECHNIK.de = www.RAILWAY-NETWORK.eu

Die einzelnen Beiträge geben die persönliche Meinung der jew. Autoren wieder.

Das Werk einschließlich aller seiner Teile ist immaterialgüterrechtlich geschützt. Es gilt das Urheberrecht der Bundesrepublik Deutschland (UrhG).

Unlizenzierte Vervielfältigung dieses Werkes ist verboten. Jede Verwertung außerhalb der Grenzen des Urheberrechtsgesetzes ist ohne schriftliche Zustimmung des Verlages unzulässig und strafbar. Das gilt insbesondere für Vervielfältigung, Übersetzungen, Mikroverfilmungen und die Einspeicherung und Verarbeitung in elektronischen Systemen bzw. Verbreitung im Internet oder Intranet. Eine elektronische Version dieses Tagungsbandes ist beim Verlag erhältlich.

Sofern Sie eine elektronische Kopie ohne dazugehörige Erlaubnis des Verlags erhalten sollten, liegt ein Rechtsverstoß gegen das Imaterialgüterrecht der Bundesrepublik Deutschland vor, der zivil- bzw. strafrechtlich verfolgt wird.

Do not duplicate or redistribute in any form. All rights reserved.

© Copyright 2015

Die Deutsche Bibliothek - CIP-Einheitsaufnahme:

Die Deutsche Bibliothek verzeichnet diese Publikation in der Deutschen Nationalbibliografie.

Detaillierte bibliografische Daten sind im Internet über <http://www.dnb.de> abrufbar.

DIES IST DIE TEILNEHMER-AUSGABE DER TAGUNGSDOKUMENTATION
TAGUNGSBAND-BESTELLUNGEN DIREKT BEIM VERLAG: WWW.IFV-BAHNTECHNIK.DE

THIS IS THE PARTICIPANT EDITION OF THE PROCEEDINGS
TO ORDER THE DOCUMENTATION PLEASE CONTACT: WWW.IFV-BAHNTECHNIK.DE



INHALTSVERZEICHNIS (Contents)

Seite (page) [Appendix]

FIRE SAFETY 2015: Fire Safety in Railway Systems: (Thematische Einführung BAHN-BRANDSCHUTZ {Grußworte}) Dipl.-Volkswirt E. SCHULZ - CEO - [IFV Bahntechnik; Berlin / Germany]; Ing. Ronald CHODÁSZ - CEO - [Verband der Bahnindustrie e.V.; Vienna /Austria]	9	[ifv] [#]
Challenges for Fire Protection Solutions in China Growing demand for customized solutions Dr. sc. techn. ETH Markus MÜLLER - Managing Director - [WAGNER Bayern GmbH; Munich / Germany]	---	[A]
Fire Protection in Rolling Stock: Control Products and Systems for Fire Safety Mag. (FH) Günter SONNLEITNER - Head of Sales for Fire Protection in Railway Rolling Stock - [Siemens AG; Vienna / Austria]	---	[B]
Experience gained from Fire Tests according to EN 45 545 and DIN 5510-2 for Testing of Seats: EN 45 545-2/ISO 5658-2, ISO 5660-1 and DIN 5510-2 Prof. Dipl. Ing. Dr. Dieter HOHENWARTER - Laborleiter Brandversuche am FB Kunststoff- und Umwelttechnik - [TGM - Staatl. Versuchsanstalt (Federal Institute of Technology); Vienna / Austria]	23	[C]
Experimental and Numerical Investigations in the Fire Behaviour of Luggage M.Sc. Dipl.-Ing. (FH) Julian BULK - Wissenschaftlicher Mitarbeiter - and Prof. Dr. Friedrich-Wilhelm WITTBECKER - [Bergische Universität Wuppertal; Fachgebiet Brand- und Explosionsschutz (Fire and Explosion Safety); Wuppertal / Germany]	39	---
Integration of a Fire Extinguishing System into the Propulsion Unit of the „INTEGRAL“ DMU Dipl.-Ing. Josef KOMETER - Managing Director and Head Business Area Engineering; Ing. Gregor SEELOS, M.Sc. - Team Leader Electro- Mechanical Engineering -; Dr.-Ing. Marcel HERMANN - Senior Engineer Vehicle Dynamics - [Molinari Rail Austria GmbH; Schwaz / Austria]	57	---
STANDARD UNI 11565 RAILWAYS VEHICLES - 12/12/2014: Design, installation, validation and maintenance of fire detection and extinguishing systems to be used in rail vehicles and technical requirements Giancarlo BIANCHI - CEO - [GASTEC-VESTA S.r.l.; Origgio / Italy]	69	---
Fire Safety in Railway Systems 2015 and beyond: Most relevant topics of FIRE SAFETY in RAILWAY SYSTEMS Dipl.-Volkswirt E. SCHULZ - CEO - [IFV Bahntechnik; Berlin / Germany]	---	[#]

**, [#] SPOKEN WORD APPLIES! - Es gilt das gesprochene Wort!*

PRINTED IN GERMANY by IFV BAHNTECHNIK e.V., Salzufer 17 - 131 SG20, 10587 Berlin
COPYRIGHT © 2015 • Do not duplicate or redistribute in any form. • All rights reserved.
www.fachpublikationen-online.de

Copyright IFV Bahntechnik

INHALTSVERZEICHNIS (Contents)

Seite (page) [Appendix]

FIRE SAFETY 2015: Railway Research Interdisciplinary Approach Dipl.-Volkswirt E. SCHULZ - CEO - [IFV Bahntechnik; Berlin / Germany]	---	[ifv]
Pure Optical False Alarm Resisting Smoke Detector: False Alarm Classification, Test Fire Results and Nuisance Aerosols Results Dr. Jan B. PHILIPP - Lead Engineer Sensorensysteme - [Apparatebau Gauting GmbH; Gilching / Germany]	79	[D]
Fire Protection of Flexible Metal/Rubber Units including Elements in Bogies: EN 45545:2013 from the Viewpoint of a Specialist of Rubber Technology Dr.-Ing. Dana GREFEN - Research & Development (Consultant); Heinz BILLROTH (Sales Manager); Frank J. SCHMITT - Director - [BATEGU Gummitechnologie GmbH & Co KG; Vienna / Austria]	---	[E]
Hot Smoke Test in Tunnels: An innovative Approach using premixed Propane Flames M.Sc. Juan Jose BLOND - Fire Safety Engineer - [Basler und Hofmann AG; Zurich / Switzerland]	---	[F]
Floating floors for rolling stock vehicles: Elastic floor bearings with high-tech Elastomers Thomas GAMSJÄGER - Product Manager - [Getzner Werkstoffe GmbH; Bürs / Austria]	---	[G]
Amphenol Rail Compound - New Material for Terminal Blocks: ARC Development and ARC Performance Dipl.-Ing. Kolja LUCKE - Export Regional Business Developer; Bruno WAFFLART - Material and Technology Survey Technician / REACH Coordinator - [Amphenol Air LB; Courbevoie / France]	---	[H]
Full Redundant Ringbus Fire Detections Systems for Railway Applications: EN 54-2, EN 54-13 (VdS) EUR ING, Ing. Reinhard HOFER - Technical Sales Manager - [NSC Sicherheitstechnik GmbH; Linz / Austria] and DI Reinhard RÖSSLER - CEO - [Rail Services International Austria GmbH; Vienna / Austria]	87	[J]
FIRE SAFETY: Concluding Remarks and Perspectives for the Future of FIRE SAFETY in RAILWAY SYSTEMS Dipl.-Volkswirt E. SCHULZ - CEO - [IFV Bahntechnik; Berlin / Germany]	---	[ifv]

ANHANG / APPENDIX

96 ff.

Vortragsfolien / Presentations **[A] - [B] - [C] - [D] - [E] - [F] - [G] - [H] - [J] - [ifv]**


**, [#] SPOKEN WORD APPLIES! - Es gilt das gesprochene Wort!*

PRINTED IN GERMANY by IFV BAHNTECHNIK e.V., Salzufer 17 - 19 / SG20, 10587 Berlin
COPYRIGHT © 2015 • Do not duplicate or redistribute in any form • All rights reserved.
www.fachpublikationen-online.de

(C)opyright IFV Bahntechnik



Fachliteratur BAHNTECHNIK AKTUELL



ifv Bahntechnik

Books in Print

IFV Bahntechnik e.V.
Salzuffer 17 - 19, SG 20
10587 Berlin / Germany
FAX: 030 31425452
email@ifv-bahntechnik.de

Verlagsinformationen online:
⇒ www.fachpublikationen-online.de

Anzahl [quantity]	BUCHTITEL [title of books in print]	Preis [price]
New!	11th Passive Safety of Rail Vehicles 2017 , ISBN 978-3-940727-55-8; [256 pages (high quality print)]	€ 210,-
	10th Passive Safety of Rail Vehicles 2015 , ISBN 978-3-940727-48-0; [228 pages (high quality print)]	€ 200,-
	9th Passive Safety of Rail Vehicles and Safe Interiors 2013 , ISBN 978-3-940727-36-7 [330 pages]	€ 160,-
	8th Passive Safety of Rail Vehicles and Interior Design (2011) , ISBN 978-3-940727-25-1; [223 pages]	€ 160,-
	SICHER REISEN: Passive Sicherheit der Reisenden und des Personals in Eisenbahnfahrzeugen; ISBN 978-3-940727-01-5; [420 Seiten im Loseblattsammelordner; 2007]	€ 280,-
Neu!	RAIL-IT 2016: Bahn-Informationstechnologie - Digitale Transformation der Bahntechnik: Hardware, Software, Schnittstellen; ISBN 978-3-940727-54-1; [230 Seiten / Farbdruck]	€ 140,-
	RAIL-IT 2014: Bahn-Informationstechnologie - Digital Rail; ISBN 978-3-940727-44-2; [152 Seiten / Farbdruck]	€ 120,-
	RAIL-IT 2011: Bahn-Informations- und Kommunikationstechnologie; ISBN 978-3-940727-28-2; [144 Seiten / Farbdruck]	€ 100,-
Neu!	TSI 2016: Bahntechnische Zulassung: Bahntechnische Zulassung und Interoperabilität; ISBN 978-3-940727-53-4; [237 Seiten / Farbdruck]	€ 120,-
Neu!	BAHNTECHNIK-SYMPOSIUM 2016: Schienengüterverkehr, Kombiniertes Verkehr & Rail-Efficiency; ISBN 978-3-940727-52-7 [219 Seiten / Farbdruck]	€ 180,-
	RAIL-FREIGHT 2014: Zukunft des Schienengüterverkehrs: Technologie, Ökonomie, Ökologie, Verkehrspolitik; ISBN 978-3-940727-41-1 [200 Seiten / Farbdruck]	€ 160,-
	Moderner Schienengüterverkehr und Intermodaler Verkehr 2012: Herausforderungen an den Güterverkehrssektor: Technologie, Ökologie, Ökonomie, Verkehrspolitik; ISBN 978-3-940727-31-2 [241 Seiten / Farbdruck]	€ 140,-
	RAIL-noise 2016: Bahnlärm und Lärmreduzierung; ISBN 978-3-940727-51-0 [219 Seiten / Farbdruck]	€ 180,-
	RAIL-noise 2014: Bahnlärm und Lärmreduzierung; ISBN 978-3-940727-42-8 [328 Seiten / Farbdruck]	€ 160,-
	BAHN-PRM 2015: Barrierefreie Mobilität im öffentlichen Personenverkehr; ISBN 978-3-940727-50-3; [195 Seiten / Farbdruck]	€ 120,-
	FIRE SAFETY 2015: 7. Symposium Bahn-Brandschutz; ISBN 978-3-940727-47-3; [210 pages]	€ 180,-
	FIRE SAFETY 2013: 6. Symposium Bahn-Brandschutz; ISBN 978-3-940727-39-8; [228 pages]	€ 180,-
	BAHN-BRANDSCHUTZ 2009: Schienenfahrzeuge und Bahn-Infrastruktur; ISBN 978-3-940727-14-5	€ 70,-
	MODERNE STRASSENBAHNEN 2015 - INFRASTRUKTUR: ISBN 978-3-940727-46-6; [249 Seiten / F.]	€ 180,-
	MODERNE STRASSENBAHNEN 2014 - FAHRZEUGE: ISBN 978-3-940727-45-9; [223 Seiten / Farbdr.]	€ 180,-
	MODERNE STRASSENBAHNEN 2012: ISBN 978-3-940727-35-0; [340 Seiten / Farbdruck]	€ 180,-
	BAHN-KLIMATECHNIK 2013: Heating, Ventilation and Air Conditioning; ISBN 978-3-940727-40-4; [232 Seiten]	€ 160,-
	Rail-Aerodynamics 2013: Aerodynamics of Trains and Infrastructure; ISBN 978-3-940727-37-4; [340 pages (high quality print)]	€ 220,-
	RAIL-Quality 2012: Qualität im Bahnwesen und IRIS-Certification; ISBN 978-3-940727-32-9; [105 Seiten / Farbdruck]	€ 100,-
	Slab Track in Europe / Feste Fahrbahn in Europa 2005; ISBN 978-3-9810797-0-8; [262 pages (high quality print)]	€ 120,-

Bestellformular:
[Order-Form]

Hiermit bestelle ich folgende Publikationen (es gelten stets die Allgemeinen Geschäftsbedingungen des IFV BAHNTECHNIK e.V.):

Name [name]

Firma / Organisation [organisation]

Straße [street]

PLZ / Ort [city - country]

Telefon [phone]

Fax [fax]

Datum [date]

Unterschrift [signature]

Stand: 23.03.2017

→ **Versandkostenfreie Lieferung innerhalb Deutschlands! Alle Preisangaben inkl. 7% Mehrwertsteuer (DVDs zu 19% MwSt.)**
(Versand nach Europa zzgl. 6,- Euro - Versandkosten nach Übersee bitte erfragen!) – [all prices are including 7% local tax (DVDs 19% tax)
prices include forwarding expenses inside Germany (shipment in Europe: add. 6,00 Euro; overseas-shipment: please ask for prices)]